

Linul, E., Marsavina, L. and Sadowski, T., 2016. Effect of density, anisotropy and temperature on dynamic compression behaviour of PUR foams. *Romanian Journal of Technical Sciences - Applied Mechanics*, 61(2), pp.176-186.

EFFECT OF DENSITY, ANISOTROPY AND TEMPERATURE ON DYNAMIC COMPRESSION BEHAVIOUR OF PUR FOAMS

EMANOIL LINUL¹, LIVIU MARSAVINA¹, TOMASZ SADOWSKI²

Abstract. Polyurethane (PUR) foam is ideally suited as packing materials or dampers for many safety applications because of its chemical and design versatility and excellent energy absorbing properties. For this purpose, this paper investigates the effect of density, material orientation (anisotropy) and temperature on the main mechanical properties of cellular materials such as rigid polyurethane (PUR) foams. The experimental tests were carried out on specimens in the form of cubes using four different densities (40, 80, 120 and 140 kg/m³). The specimens were subjected to uniaxial dynamic compression with loading speed of 1.67 m/s, using different temperature (20, 60, 100°C). Significant differences in the behavior of the foam were observed depending on the density and testing conditions. Over the range of examined densities, the yield and plateau stresses as well as the Young modulus of the foam exhibited polynomial power-law dependencies with respect to density and have found that one of the most significant effects of mechanical properties in compression of rigid polyurethane foams is the density. In the process of absorbing impact energy, cell walls deform plastically and get damaged. After compression tests the foam shows a plastic collapse of cells, which increases the stress delivered to an almost constant strain (known as densification). In the moment of densification, due to the filling of the gaps in the foam, this one acts almost like a solid material.

Keywords: PUR foams, dynamic compression, density, anisotropy, temperature.

1. INTRODUCTION

Rigid polyurethane foams are widely used in engineering applications because they have certain properties that cannot be elicited from many homogeneous solids [1, 2]. Foams can be compressed to a relatively high strain under an approximately constant load [3–6]. This makes them very useful for impact absorption because they can dissipate significant kinetic energy while limiting the magnitude of the force transferred to more fragile components that they shield [7–9]. Hence, they are used in the packaging of electronic products and in car bumpers. The strength, stiffness

¹ “Politehnica” University of Timisoara, Department of Mechanics and Strength of Materials, Romania

² Lublin University of Technology, Department of Solid Mechanics, Poland

and weight of foams depend on their density, which can be varied [10–13]. Hence, the properties of foams can be controlled, making them attractive in structural application requiring particular strength or stiffness to weight ratios [14–19].

Foam materials show a brittle fracture in tension [20–23], but crush in compression. Research on characterization of cellular materials under compressive loading conditions has been widely reported as in Refs [24–29]. The various properties and attributes investigated include energy absorption, density, cell structure, yield criteria, strain rate, energy efficiency. Avalle *et al.* [24] presented an optimization procedure in order to identify the micromechanical parameters from uniaxial compression test of different types of foams. The effect of the density and filler size was also investigated in [25]. Ramsteiner *et al.* [30] analyzed the parameters influencing the mechanical properties of foam. The following parameters were identified and studied: the structure of the foam, the matrix material of the foam, the density of the foam, cell orientation and testing temperature. Linul *et al.* [31] presented a comparison, of stress–strain response in compression, between experimental results and micromechanical modelling for PUR foams. The crush behaviour of Rohacell structural foam was investigated by Li *et al.* [32]. Tu *et al.* [33] presented the plastic deformations of PUR foam under static compressive loading and proposed a theoretical approach to describe the deformation localization.

The mechanical behaviour of rigid polyurethane foams under compressive loading is probably the primary property that distinguishes it from non-cellular solids. The use of foams in kinetic energy absorption and structural applications, whereby they are subjected to static and dynamic loading, motivates the need to study their mechanical properties [34].

2. EXPERIMENTAL PROCEDURE

For the characterization of mechanical behaviour on dynamic compression loading, rigid polyurethane foams used in the experimental program had the following densities: 40, 80, 120 and 140 kg/m³. Fig.1 presents a comparison of used specimens between the initial shape, undistorted (before loading) and the final shape, deformed (after loading).



Fig. 1 – Specimens used in the experimental program.

The specimens were subjected to uniaxial dynamic compression with loading speed of 1.67 m/s, using different temperatures (20, 60, 100°C). For each test type five specimens were used. Experimental tests were made on the Strength of Materials Laboratory from Lublin University of Technology, Poland. Tests were carried on an Instron-Dynatup impact testing machine.

Mechanical behaviour of rigid PUR foams under compression tests was determined according to the ASTM D1621-00, Standard Test Method for Compressive Properties of Rigid Cellular Plastics [35].

3. RESULTS AND DISCUSSIONS

The present work presents a detailed study of the influence of density, material orientation (anisotropy) and temperature on the main mechanical properties of rigid PUR foams, subjected to dynamic compression loads. These parameters such as Young's modulus, yield stress, plateau stress and densification have a very important role in the real applications of these materials and due to this reason in the following it will be presented the foam behaviour under different loading and temperature conditions. From data provided by the test machine, were drawn the conventional characteristic curves for the tested specimens [1, 24]. Figure 2 shows a comparison of typical stress-strain curves for different densities of polyurethane foam (40, 80, 120 and 140 kg/m³), subjected to dynamic compression. Presented curves were obtained from a perpendicular load to the forming plane (out-of-plane direction) at a temperature of 20°C.

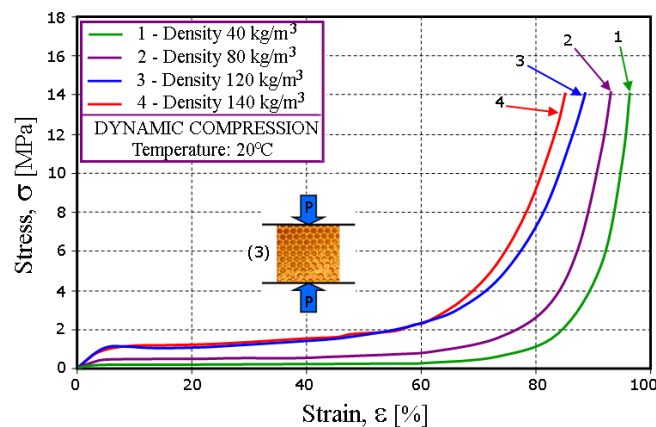


Fig. 2 – Typical stress-strain curves. Effect of density.

On the recorded stress-strain diagrams the following regions can be identified: the first part of the curve shows linear-elastic behaviour up to yield (up

to a strain of 5% approximately), a small softening in stress after yield, a plateau after yield (between 10–50%), and in the end there is an increase in stress without a significant increases in strain, commonly known as densification (above 50% strain). Variations of mentioned mechanical properties with density for out of plane direction – direction (3) – are presented in Figs. 3–5.

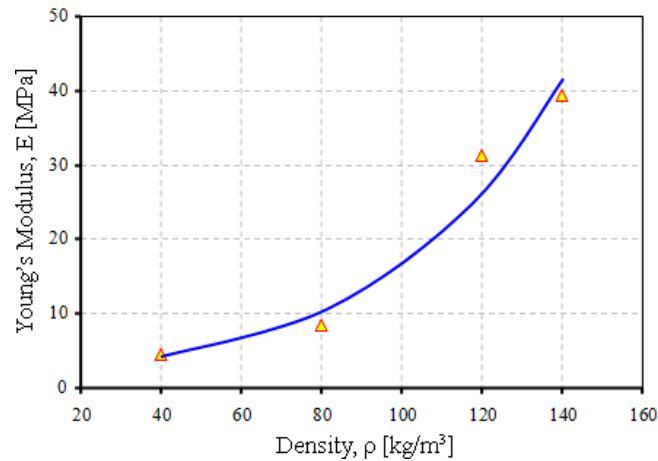


Fig. 3 – Young's modulus variation with density. Effect of density.

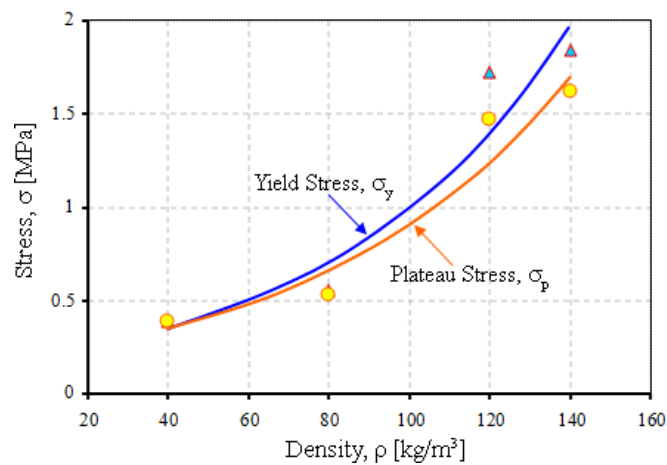


Fig. 4 – Yield and plateau stress variations with density. Effect of density.

All of these figures (Figs. 2–5) show a significant increase of mechanical characteristics with increasing of density, which means that the density has a major role in determining the mechanical properties in compression. The Young's modulus difference between the highest and lowest density foam is about 10 times, when yield stress and plateau stress increases about 4 times. On the other hand, as

can be seen from Fig. 5 it was found that only densification decreases with increasing of foams density. In this case, densification decreases from a value of about 67% to a value of about 57%.

Foam anisotropy is a very important parameter of foam and should be considered for both in practical applications and in the modelling of the mechanical properties. Thus, choosing properly this parameter, we can obtain the desired characteristics for practical applications.

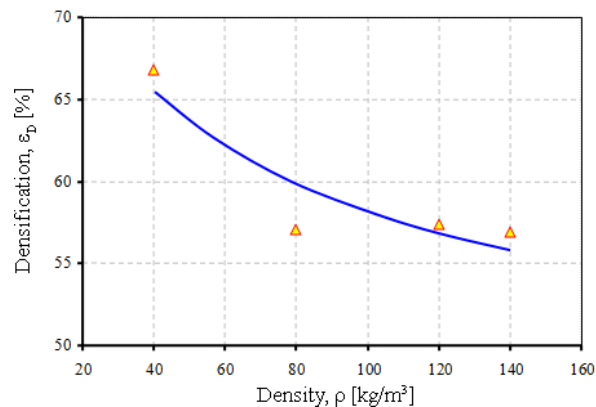


Fig. 5 – Densification variation with density.
Effect of density.

Figure 6 presents the influence of forming plane and loading direction on dynamic compression while in Fig. 7 is shown the sampling of the specimens from a rectangular plate, respectively the loading direction according to the formation plane of the foam. In this case was studied a foam with density of 140 kg/m³ at room temperature.

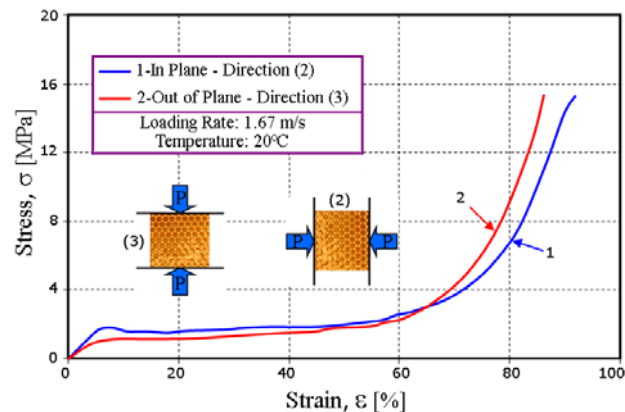


Fig. 6 – Typical stress-strain curves. Effect of forming plane.

For the in-plane loading direction a constant plateau was obtained, while for out-of-plane loading direction the plateau has a linear hardening for the same foam density (Fig. 6).

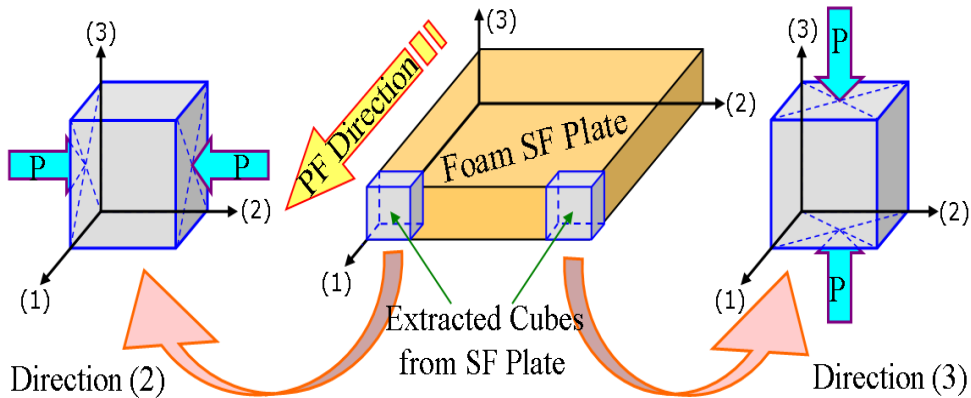


Fig. 7 – The sampling of the cube specimens from a rectangular plate.

Variations of studied mechanical properties with density (four different densities) for out-of-plane direction – direction (3) and in-plane direction – direction (2) are presented in Figs. 8–11.

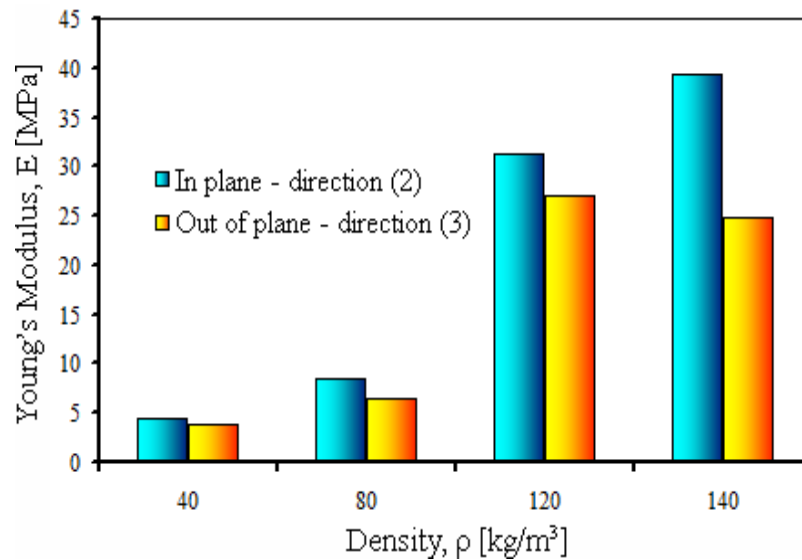


Fig. 8 – Young's modulus versus density. Effect of forming plane.

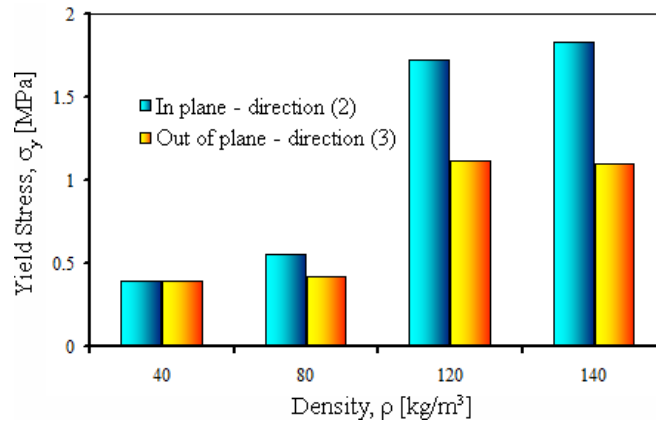


Fig. 9 – Yield stress versus density. Effect of forming plane.

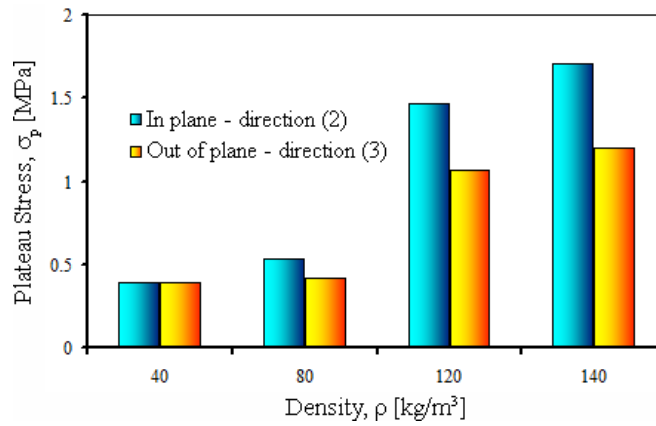


Fig. 10 – Plateau stress versus density. Effect of forming plane.

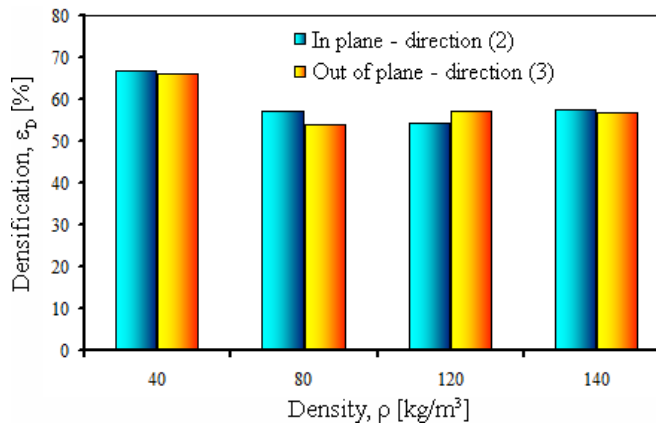


Fig. 11 – Densification versus density. Effect of forming plane.

Loading direction has a significant contribution to the compressive mechanical properties; this aspect highlights the anisotropic behaviour of foam. Anisotropy aspect is particularly strong for high-density foam (140 kg/m^3), while in the case of low-density foams (40 kg/m^3) is almost unobservable. In this case (for 140 kg/m^3), the material is highly anisotropic with a much higher in-plane than out-of-plane, as follows: the Young's modulus increases from 24.82 MPa to 39.43 MPa , the yield stress increases from 1.10 MPa to 1.83 MPa and plateau stress increases from 1.20 MPa to 1.71 MPa , while the densification remains the same (approximately 57%).

Considering both sudden temperature and different areas of use of these materials is important to carrying out a study of the effect of temperature on the mechanical behaviour. This study was performed for four different rigid PUR foams at three different temperatures: 20 , 60 and 100°C and two loading directions (in-plane and out-of-plane). For this purpose and for easier understanding of the behaviour, Fig. 12 shows the effect of temperature on the stress-strain curves only for 140 kg/m^3 foam density (load has been applied in-plane).

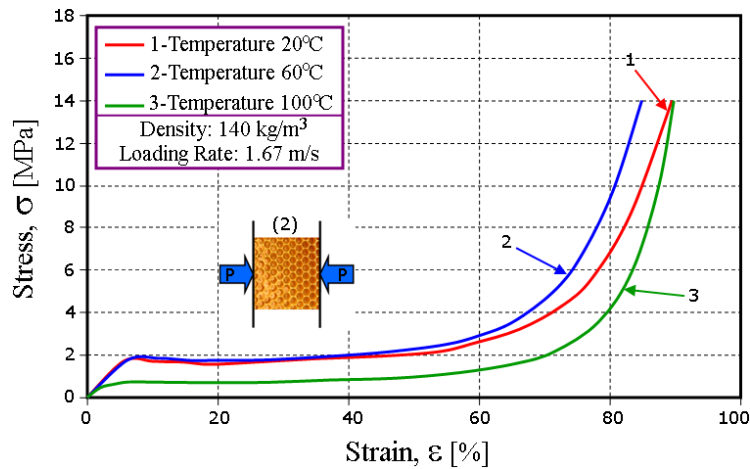


Fig. 12 – Typical stress-strain curves. Effect of temperature.

According to the results shown in Fig.12 it can be seen that at room temperature (20°C) and a temperature of 60°C the foam behaviour is approximately the same, while at higher temperatures (100°C), foam changes significant its properties. It should be noted that for polyurethane foams temperature of 100°C can be considered high because they have a melting temperature around 150°C .

4. CONCLUSIONS

The experimental study was carried out on four different density of rigid PUR foams (40, 80, 120 respectively 140 kg/m³), and presents a comparison of the stress-strain response in dynamic compression. After the experimental investigations the following conclusions can be drawn:

- It can easily observed that with increasing of density we obtain a significant increase of mechanical properties, which means that the density has an important role in determining the dynamic compressive mechanical behaviour (Figs. 2–4).
- The loading direction has a major influence on the mechanical properties in dynamic conditions, clear evidence of anisotropic behaviour of foam. For the same foam density in-plane loading direction a constant plateau was obtained, while for out-of-plane load the plateau presents a linear hardening (Figs. 8–11).
- According to the results presented in Fig. 12, it can be observed that at lowest temperatures (20 and 60°C), the behaviour of foam is approximately the same, while at high temperature (100°C), foam shown a major change in their mechanical properties.
- In the process of absorbing impact energy, cell walls deform plastically and get damaged. After compression tests the foam shows a plastic collapse of cells, which increases the stress delivered to an almost constant strain (known as densification). In the moment of densification, due to the filling of the gaps in the foam, this one acts almost like a solid material.

Acknowledgements. The authors are grateful to Dr. Marcin Kniec from Lublin University of Technology for his help in performing the experiments.

Received on June 29, 2016

REFERENCES

1. GIBSON, L.J. ASHBY, M.F., *Cellular solids, Structure and properties*, Second edition, Press Syndicate of the University of Cambridge, 1997.
2. AJDARI, A., *Mechanical behaviour of cellular structures a finite element study*, Master on Science in Mechanical Engineering, Northeastern University, Boston, Massachusetts, 2008.
3. MARSAVINA, L., KOVACIK, J., LINUL, E., *Experimental validation of micromechanical models for brittle aluminium alloy foam*, Theor. Appl. Fract. Mech., **83**, pp. 11–18, 2016.
4. LINUL, E., ŞERBAN, D.A., MARSAVINA, L., KOVACIK, J., *Low-cycle fatigue behaviour of ductile closed-cell aluminium alloy foams*, Fatigue Fract. Eng. Mater. Struct., 2016, <http://dx.doi.org/10.1111/ffe.12535>.
5. KOVÁČIK, J., JERZ, J., MINÁRIKOVÁ, N., MARSAVINA, L., LINUL, E., *Scaling of compression strength in disordered solids: metallic foams*, Frattura ed Integrità Strutturale, **36**, pp. 55–62, 2016.

6. MARSAVINA, L., CONSTANTINESCU, D.M., LINUL, E., STUPARU, F.A., APOSTOL, D.A., *Experimental and numerical crack paths in PUR foams*, Eng. Fract. Mech., **167**, pp. 68–83, 2016.
7. LINUL, E., ŞERBAN, D.A., MARSAVINA, L., SADOWSKI, T., *Assessment of collapse diagrams of rigid polyurethane foams under dynamic loading conditions*, Arch. Civ. Mech. Eng., **17**, 3, pp. 457–466, 2017.
8. LINUL, E., ŞERBAN, D.A., VOICONI, T., MARSAVINA, L., SADOWSKI, T., *Energy-absorption and efficiency diagrams of rigid PUR foams*, Key Engineering Materials, **601**, pp. 246–249, 2014.
9. ŞERBAN, D.A., LINUL, E., VOICONI, T., MARSAVINA, MODLER, N., *Numerical evaluation of two-dimensional micromechanical structures of anisotropic cellular materials: case study for polyurethane rigid foams*, Iran. Polym. J., **24**, pp. 515–529, 2015.
10. LINUL, E., MARSAVINA, L., KOVACIK, J., *Collapse mechanisms of metal foam matrix composites under static and dynamic loading conditions*, Mat. Sci. Eng. A-Struct., **690**, pp. 214–224, 2017, <http://dx.doi.org/10.1016/j.msea.2017.03.009>.
11. LINUL, E., MARSAVINA, L., *Assessment of sandwich beams with rigid polyurethane foam core using failure-mode maps*, Proc. Rom. Acad. A, **16**, 4, pp. 522–530, 2015.
12. ŞERBAN, D.A., LINUL, E., SARANDAN, S., MARSAVINA, L., *Development of parametric Kelvin structures with closed cells*, Solid State Phenomena, **254**, pp. 49–54, 2016.
13. MARSAVINA, L., LINUL, E., VOICONI, T., NEGRU, R., *Experimental investigations and numerical simulations of notch effect in cellular plastic materials*, IOP Conference Series: Materials Science and Engineering, **123**, 1, 012060, 2016.
14. BIRSAN, M., SADOWSKI, T., MARSAVINA, L., LINUL, E., PIETRAS, D., *Mechanical behavior of sandwich composite beams made of foams and functionally graded materials*, Int. J. Solids Struct., **50**, pp. 519–530, 2013.
15. MARSAVINA, L., CONSTANTINESCU, D.M., LINUL, E., VOICONI, T., APOSTOL, D.A., SADOWSKI, T., *Evaluation of mixed mode fracture for PUR foams*, Procedia Materials Science, **3**, pp. 1342–1352, 2014.
16. VOICONI, T., NEGRU, R., LINUL, E., MARSAVINA, L., FILIPESCU, H., *The notch effect on fracture of polyurethane materials*, Frattura ed Integrità Strutturale, **30**, pp. 101–108, 2014.
17. MARSAVINA, L., LINUL, E., VOICONI, T., CONSTANTINESCU, D.M., APOSTOL, D.A., *On the crack path under mixed mode loading on PUR foams*, Frattura ed Integrità Strutturale, **34**, pp. 444–453, 2015.
18. NEGRU, R., MARSAVINAA, L., VOICONI, T., LINUL, E., FILIPESCU, H., BELGIU, G., *Application of TCD for brittle fracture of notched PUR materials*, Theor. Appl. Fract. Mech. **80**, pp. 87–95, 2015.
19. MARSAVINA L., CONSTANTINESCU, D.M., LINUL, E., VOICONI, T., APOSTOL, D.A., *Shear and mode II fracture of PUR foams*, Eng. Fail. Anal., **58**, pp. 465–476, 2015.
20. LINUL, E., MARSAVINA, L., *Prediction of fracture toughness for open cell polyurethane foam by finite-element micromechanical analysis*, Iranian Pol. J., **20**, 9, pp. 735–746, 2011.
21. LINUL, E., VOICONI, T., MARSAVINA, L., *Determination of mixed mode fracture toughness of PUR foams*, Structural Integrity and Life, **14**, 2, pp. 87–92, 2014.
22. MARSAVINA, L., CONSTANTINESCU, D.M., LINUL, E., APOSTOL, D.A., VOICONI, T., SADOWSKI, T., *Refinements on fracture toughness of PUR foams*, Eng. Fract. Mech., **129**, pp. 54–66, 2014.
23. MARSAVINA, L., LINUL, E., *Fracture toughness of polyurethane foams. Experimental versus micromechanical models*, Fracture of Materials and Structures from Micro to Macro Scale; 18th European Conference on Fracture, Dresden, Germany, August 30 – September 03, 2010.
24. AVALLE, M., *Characterization of polymeric structural foams under compressive impact loading by means of energy-absorption*, Int. J. Impact Eng., **25**, pp. 455–472, 2001.
25. AVALLE, M., BELINGARDI, G., IBBA, G., *Mechanical models of cellular solids: Parameters identification from experimental tests*, Int. J. Impact Eng., **34**, pp. 3–27, 2007.

26. SAHA, M.C., MAHFUZ, H., CHARAVARTHY, U.K., UDDIN, M., KABIR, M.E., JEELANI, S., *Effect of density, microstructure and strain rate on compression behavior of polymeric foams*, Mat. Sci. Eng. A-Struct., **A406**, pp. 328–336, 2005.
27. OUELLET, S., CRONIN, D., *Compressive Response of Polymeric Foams Under Quasi-static, Medium and High Strain Rate Conditions*, Polym. Test., **25**, pp. 731–743, 2006.
28. LINUL, E., VOICONI, T., MARSAVINA, L., SADOWSKI, T., *Study of factors influencing the mechanical properties of polyurethane foams under dynamic compression*, Journal of Physics: Conference Series, **451**, 012002, 2013.
29. LINUL, E., MARSAVINA, L., SADOWSKI, T., KNEĆ, M., *Size Effect on Fracture Toughness of Rigid Polyurethane Foams*, Solid State Phenomena, **188**, pp. 205–210, 2012.
30. RAMSTEINER, F., FELL, N., FORSTER, S., *Testing the deformation behaviour of polymer foams*, Polym. Test., **20**, pp. 661–670, 2001.
31. LINUL, E., MARSAVINA, L., CERNESCU, A.V., *Effect of loading speed, the direction of formation and density of rigid polyurethane foams subjected to compression*, Acta Tehnica Napocensis, Series: Mechanical Engineering. Material Science, **53**, pp. 311–316, 2010.
32. LI, Q.M., MAGKIRIADIS, I., HARRIGAN, J.J., *Compressive Strain at the Onset of Densification of Cellular Solids*, Journal of Cellular Plastics, **42**, pp. 371–392, 2006.
33. TU, Z.H., SHIM, V.P.W., LIM, C.T., *Plastic deformation modes in rigid polyurethane foam under static loading*, Int. J. Solids Struct., **38**, pp. 9267–9279, 2001.
34. MARSAVINA, L., LINUL, E., VOICONI, T., SADOWSKI, T., *A comparison between dynamic and static fracture toughness of polyurethane foams*, Polym. Test., **32**, pp. 673–680, 2013.
35. *** ASTM D1621-00 Standard Test Method for Compressive Properties of Rigid Cellular Plastics.